

表題 : $Ce_3T_4Sn_{13}$ ($T = Co, Rh, Ru$) に現れるカイラルフェルミオンによる磁気構造と励起

Field-induced magnetic correlations in chiral lattice semimetals $Ce_3Co_4Sn_{13}$ and $Ce_3Rh_4Sn_{13}$

K. Iwasa¹, Y. Otomo², K. Suyama², A. Goukasov³, B. Gillon³, J.-M. Mignot³

Frontier Research Center for Applied Atomic Sciences, Ibaraki University, Japan¹

Department of Physics, Tohoku University, Japan²

Laboratoire Léon Brillouin, CEA-CNRS, CEA/Saclay, France³

Electronic correlation phenomena have been central topics of solid-state physics. In the case of f -electron systems, the c - f hybridization effect has been a key issue. In addition, topological natures of electrons have recently been attractive recently: the electronic state of topological insulators of surface states and graphene are expressed as massless Dirac or Weyl fermions. A theoretical study have proposed a way to find three-dimensional (3D) bulk Weyl fermions in chiral symmetry lattices (J. L. Manñs, *Phys. Rev. B* **85**, 155118 (2012)). It is an attractive subject to find such chiral fermion systems and electronic correlations between the chiral fermions and the f electrons.

$Ce_3Co_4Sn_{13}$ has been reported to undergo a structural phase transition at 160 K (C. S. Lue et al., *Phys. Rev. B* **85**, 205120 (2012)), and similar phenomena are also suggested for $Ce_3Rh_4Sn_{13}$ (A. Ślebarski et al., *Phys. Rev. B* **86**, 155122 (2012)). We evidenced low-temperature crystal structure categorized in the chiral space group $I2_13$ below the structural phase transitions at 160 and 352 K in $Ce_3Co_4Sn_{13}$ and $Ce_3Rh_4Sn_{13}$, respectively (Y. Otomo et al., *Phys. Rev. B* **94**, 075109 (2016)). The electrical resistivity data of $Ce_3Co_4Sn_{13}$ and $Ce_3Rh_4Sn_{13}$ are almost independent of temperature, in contrast to metallic behaviors of the La-based reference materials. These structural finding and transport property are expected to be signatures for the formation of Weyl semimetal state. The electronic Sommerfeld coefficients of these compounds reach approximately 4 J/(mol-Ce K²) at 1 K (A. L. Cornelius et al., *Physica B* **378-380**, 113 (2006), A. Ślebarski et

al., *Phys. Rev. B* **86**, 205113 (2012), E. L. Thomas et al., *J. Solid State Chem.* **179**, 1642 (2006)). This fact was understood as HF systems. However, our recent inelastic neutron scattering experiment revealed the emergence of spin excitations in the range up to 1 meV below 20 K (K. Iwasa et al., *Phys. Rev. B* **95**, 195156 (2017)), which originates from the crystal-electric-field (CEF) doublet ground state. Therefore, coherent spin dynamics emerge in the semimetal chiral phase. On the other hand, $Ce_3Co_4Sn_{13}$ and $Ce_3Rh_4Sn_{13}$ do not exhibit any magnetic ordering down to 0.5 K (K. Iwasa et al., in preparation), and previous study on $Ce_3Co_4Sn_{13}$ reported the field-induced antiferromagnetic correlations at 4.2 K (A. D. Christianson et al., *Physica B* **403**, 909 (2008)). Based on the $I2_13$ structure, the two inequivalent Wyckoff sites for the Ce ions take different CEF schemes (K. Iwasa et al., *Phys. Rev. B* **95**, 195156 (2017)). Thus, the magnetic-field-induced antiferromagnetic correlation can be understood different magnetic moments at the two Ce-ion sites. In order to examine such scenario for the Ce $4f$ -electron state, we performed polarized neutron diffraction measurements under the magnetic fields up to 6 T below 20 K, by using the hot-neutron diffractometer 5C1 installed in the Orphée reactor of Laboratoire Léon Brillouin.

Figure 1 shows measured intensity maps within the $[1\ 0\ 0]$ - $[0\ 1\ 0]$ reciprocal plane perpendicular to the applied magnetic fields of 6 T at measurement temperature of 2 K for $Ce_3Co_4Sn_{13}$. The measured results for the up (upper panel) and down (lower panel) spin polarizations of the incident neutron are not identical with each

使用施設 : JRR-3M , 装置 : 6G:TOPAN

分野 : Strongly Correlated Electron Systems

other, in particular for the reciprocal-lattice region with h and $k < 10$. Similar polarization dependence was also observed for $\text{Ce}_3\text{Rh}_4\text{Sn}_{13}$. Such results indicate characteristic magnetic-moment distribution, the magnetic-scattering neutron wave from which interferes with the nuclear-scattering wave. Preliminary analysis for the flipping-ratio data shown in Fig. 1 based on the Cambridge crystallography subroutines give the magnetic moments of 1.5 and $0.9\mu_B$ at the two inequivalent Ce-ion sites. This result is consistent with the aforementioned structural and magnetic properties in the chiral phase.

We thank J.-L. Meuriot for technical support on performing the polarized neutron diffraction measurements. The experiments were supported by General User Program for Neutron Scattering Experiments, Institute for Solid State Physics, The University of Tokyo, at JRR-3, Japan Atomic Energy Agency, Tokai, Japan.

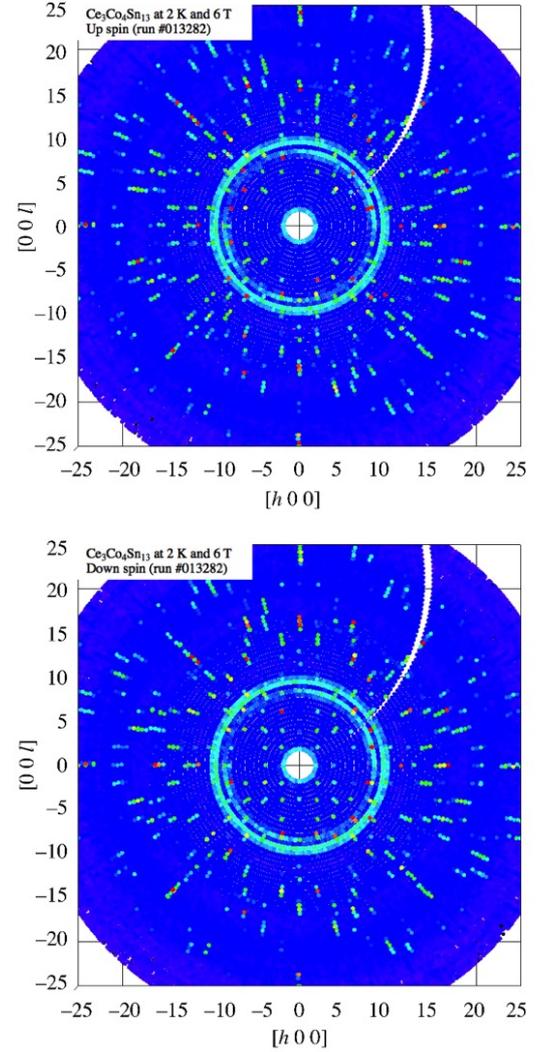


Fig. 1. Diffraction-intensity maps within the [100]-[010] reciprocal plane perpendicular to the applied magnetic fields of 6 T at measurement temperature of 2 K.